

Crystal Systems

Session: 2021-2022

Course code: PHY 3205

Course title: Solid State Physics I

Bachelor of Science with Honours in Physics

Jashore University of Science and Technology

Content

Classification of Materials; Lattice; Crystal and its Symmetries; Classification of Crystals, Unit Cell; Basis vector; Bravais Lattice; Miller Indices; Crystal Structures; Calculation of Lattice Points; Packing Factor; Inter-planar Spacing; Reciprocal Lattice; Bragg's Diffraction; Brillouin Zones; Atomic Form Factor; Structure Factor.

References

Introduction to Solid State Physics – Charles Kittel

Solid State Physics – Neil W. Ashcroft, N. David Mermin

Elementary Solid State Physics: Principles and Applications – M. Ali Omar

1

Crystal Structure

PERIODIC ARRAYS OF ATOMS	3
Lattice translation vectors	4
Basis and the crystal structure	5
Primitive lattice cell	6
FUNDAMENTAL TYPES OF LATTICES	6
Two-dimensional lattice types	8
Three-dimensional lattice types	9
INDEX SYSTEM FOR CRYSTAL PLANES	11
SIMPLE CRYSTAL STRUCTURES	13
Sodium chloride structure	13
Cesium chloride structure	14
Hexagonal close-packed structure	15
Diamond structure	16
Cubic zinc sulfide structure	17
DIRECT IMAGING OF ATOMIC STRUCTURE	18
NONIDEAL CRYSTAL STRUCTURES	18
Random stacking and polytypism	19
CRYSTAL STRUCTURE DATA	19
SUMMARY	22
PROBLEMS	22
1. Tetrahedral angles	22
2. Indices of planes	22
3. Hcp structure	22

UNITS: $1 \text{ \AA} = 1 \text{ angstrom} = 10^{-8} \text{ cm} = 0.1 \text{ nm} = 10^{-10} \text{ m}.$

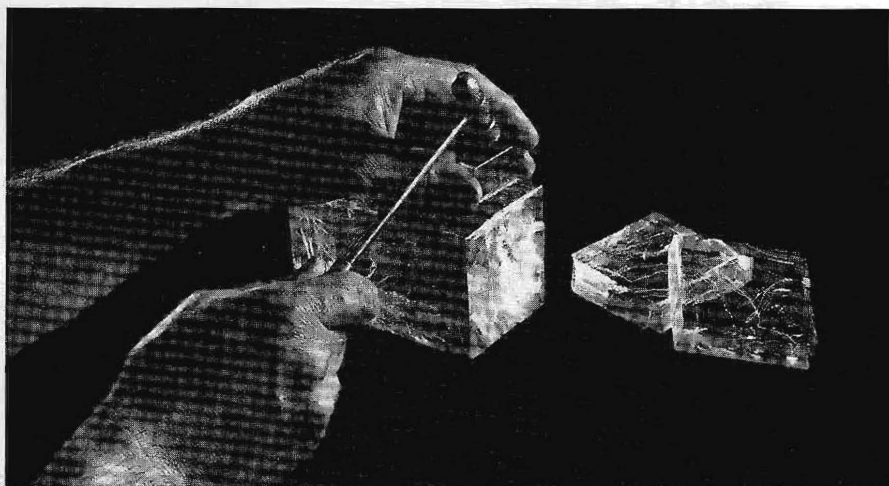
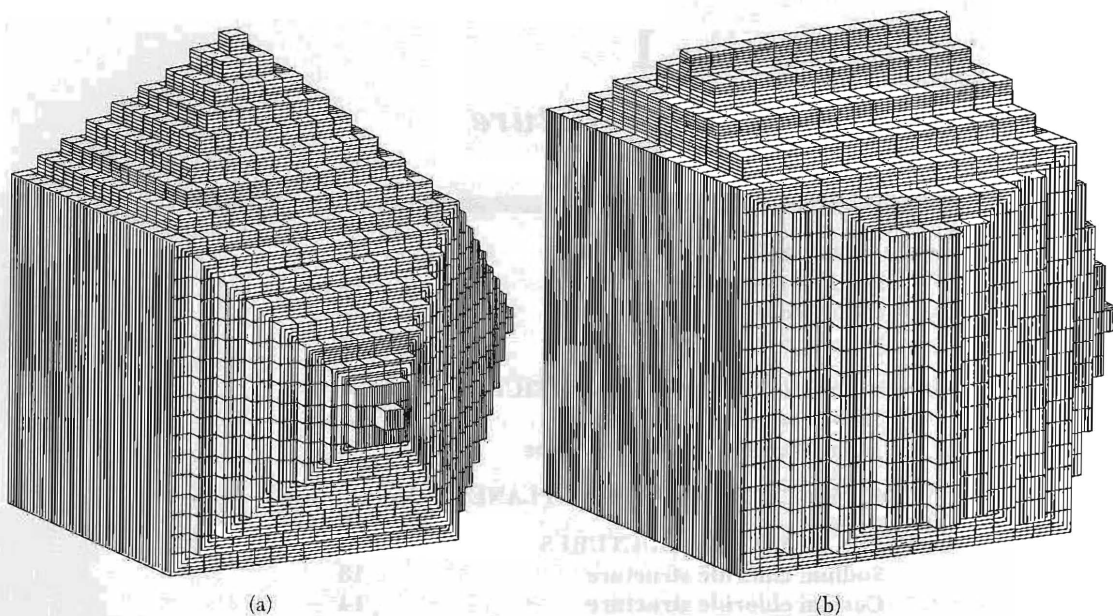


Figure 1 Relation of the external form of crystals to the form of the elementary building blocks. The building blocks are identical in (a) and (b), but different crystal faces are developed. (c) Cleaving a crystal of rock salt.

CHAPTER 1: CRYSTAL STRUCTURE

PERIODIC ARRAYS OF ATOMS

The serious study of solid state physics began with the discovery of x-ray diffraction by crystals and the publication of a series of simple calculations of the properties of crystals and of electrons in crystals. Why crystalline solids rather than noncrystalline solids? The important electronic properties of solids are best expressed in crystals. Thus the properties of the most important semiconductors depend on the crystalline structure of the host, essentially because electrons have short wavelength components that respond dramatically to the regular periodic atomic order of the specimen. Noncrystalline materials, notably glasses, are important for optical propagation because light waves have a longer wavelength than electrons and see an average over the order, and not the less regular local order itself.

We start the book with crystals. A crystal is formed by adding atoms in a constant environment, usually in a solution. Possibly the first crystal you ever saw was a natural quartz crystal grown in a slow geological process from a silicate solution in hot water under pressure. The crystal form develops as identical building blocks are added continuously. Figure 1 shows an idealized picture of the growth process, as imagined two centuries ago. The building blocks here are atoms or groups of atoms. The crystal thus formed is a three-dimensional periodic array of identical building blocks, apart from any imperfections and impurities that may accidentally be included or built into the structure.

The original experimental evidence for the periodicity of the structure rests on the discovery by mineralogists that the index numbers that define the orientations of the faces of a crystal are exact integers. This evidence was supported by the discovery in 1912 of x-ray diffraction by crystals, when Laue developed the theory of x-ray diffraction by a periodic array, and his coworkers reported the first experimental observation of x-ray diffraction by crystals. The importance of x-rays for this task is that they are waves and have a wavelength comparable with the length of a building block of the structure. Such analysis can also be done with neutron diffraction and with electron diffraction, but x-rays are usually the tool of choice.

The diffraction work proved decisively that crystals are built of a periodic array of atoms or groups of atoms. With an established atomic model of a crystal, physicists could think much further, and the development of quantum theory was of great importance to the birth of solid state physics. Related studies have been extended to noncrystalline solids and to quantum fluids. The wider field is known as condensed matter physics and is one of the largest and most vigorous areas of physics.

Lattice Translation Vectors

An ideal crystal is constructed by the infinite repetition of identical groups of atoms (Fig. 2). A group is called the **basis**. The set of mathematical points to which the basis is attached is called the **lattice**. The lattice in three dimensions may be defined by three translation vectors \mathbf{a}_1 , \mathbf{a}_2 , \mathbf{a}_3 , such that the arrangement of atoms in the crystal looks the same when viewed from the point \mathbf{r} as when viewed from every point \mathbf{r}' translated by an integral multiple of the \mathbf{a} 's:

$$\mathbf{r}' = \mathbf{r} + u_1\mathbf{a}_1 + u_2\mathbf{a}_2 + u_3\mathbf{a}_3. \quad (1)$$

Here u_1, u_2, u_3 are arbitrary integers. The set of points \mathbf{r}' defined by (1) for all u_1, u_2, u_3 defines the lattice.

The lattice is said to be **primitive** if any two points from which the atomic arrangement looks the same always satisfy (1) with a suitable choice of the integers u_i . This statement defines the **primitive translation vectors** \mathbf{a}_i . There is no cell of smaller volume than $\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3$ that can serve as a building block for the crystal structure. We often use the primitive translation vectors to define the **crystal axes**, which form three adjacent edges of the primitive parallelepiped. Nonprimitive axes are often used as crystal axes when they have a simple relation to the symmetry of the structure.

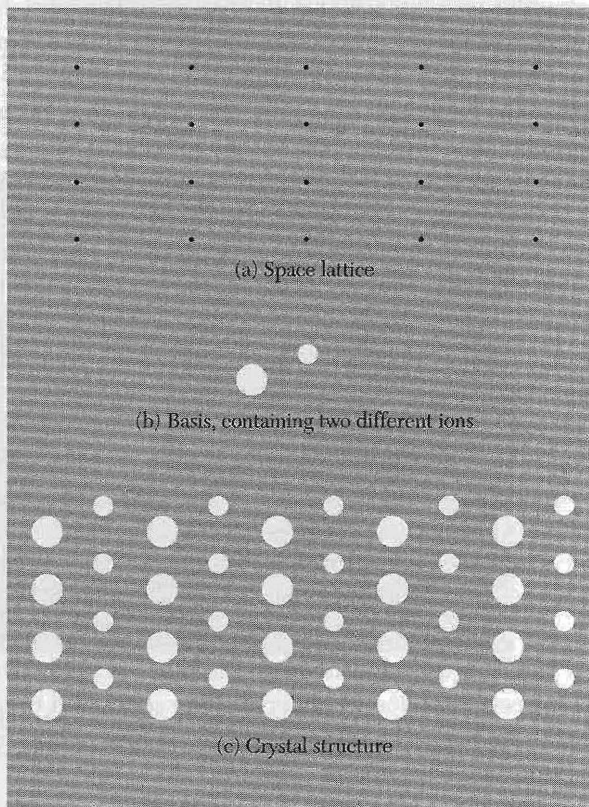


Figure 2 The crystal structure is formed by the addition of the basis (b) to every lattice point of the space lattice (a). By looking at (c), one can recognize the basis and then one can abstract the space lattice. It does not matter where the basis is put in relation to a lattice point.

Basis and the Crystal Structure

The **basis** of the crystal structure can be identified once the crystal axes have been chosen. Figure 2 shows how a crystal is made by adding a basis to every lattice point—of course the lattice points are just mathematical constructions. Every basis in a given crystal is identical to every other in composition, arrangement, and orientation.

The number of atoms in the basis may be one, or it may be more than one. The position of the center of an atom j of the basis relative to the associated lattice point is

$$\mathbf{r}_j = x_j \mathbf{a}_1 + y_j \mathbf{a}_2 + z_j \mathbf{a}_3. \quad (2)$$

We may arrange the origin, which we have called the associated lattice point, so that $0 \leq x_j, y_j, z_j \leq 1$.


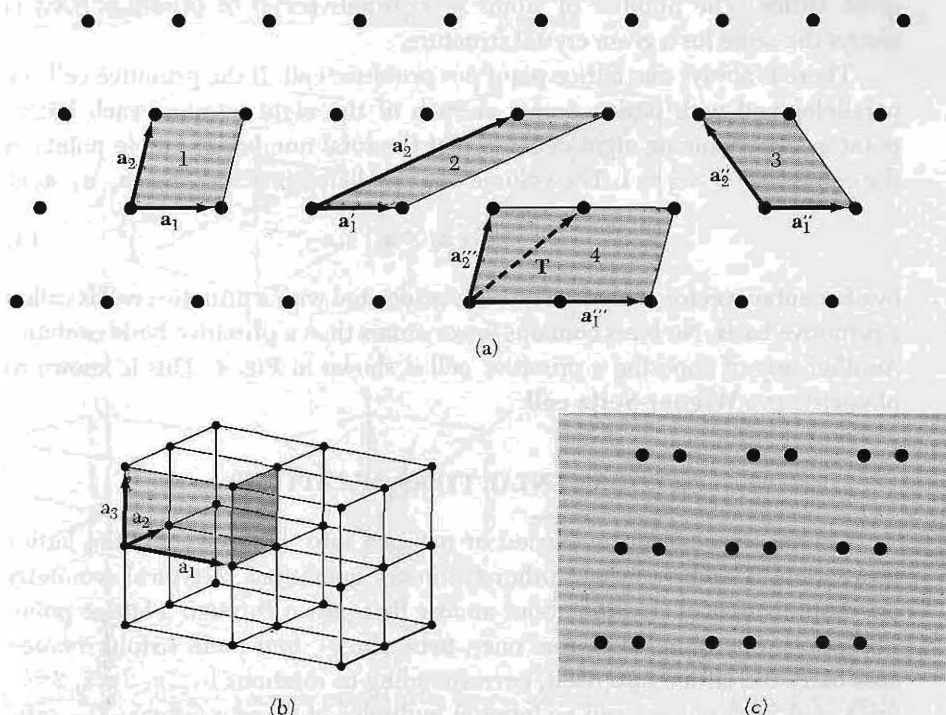


Figure 3a Lattice points of a space lattice in two dimensions. All pairs of vectors $\mathbf{a}_1, \mathbf{a}_2$ are translation vectors of the lattice. But $\mathbf{a}_1'', \mathbf{a}_2''$ are not primitive translation vectors because we cannot form the lattice translation \mathbf{T} from integral combinations of \mathbf{a}_1'' and \mathbf{a}_2'' . The other pairs shown of \mathbf{a}_1 and \mathbf{a}_2 may be taken as the primitive translation vectors of the lattice. The parallelograms 1, 2, 3 are equal in area and any of them could be taken as the primitive cell. The parallelogram 4 has twice the area of a primitive cell.

Figure 3b Primitive cell of a space lattice in three dimensions.

Figure 3c Suppose these points are identical atoms: Sketch in on the figure a set of lattice points, a choice of primitive axes, a primitive cell, and the basis of atoms associated with a lattice point.

Figure 4 A primitive cell may also be chosen following this procedure: (1) draw lines to connect a given lattice point to all nearby lattice points; (2) at the midpoint and normal to these lines, draw new lines or planes. The smallest volume enclosed in this way is the Wigner-Seitz primitive cell. All space may be filled by these cells, just as by the cells of Fig. 3.

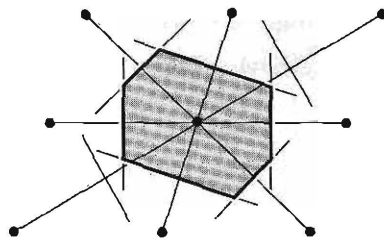

Primitive Lattice Cell

The parallelepiped defined by primitive axes \mathbf{a}_1 , \mathbf{a}_2 , \mathbf{a}_3 is called a **primitive cell** (Fig. 3b). A primitive cell is a type of cell or unit cell. (The adjective unit is superfluous and not needed.) A cell will fill all space by the repetition of suitable crystal translation operations. A primitive cell is a minimum-volume cell. There are many ways of choosing the primitive axes and primitive cell for a given lattice. The number of atoms in a primitive cell or primitive basis is always the same for a given crystal structure.

There is always one lattice point per primitive cell. If the primitive cell is a parallelepiped with lattice points at each of the eight corners, each lattice point is shared among eight cells, so that the total number of lattice points in the cell is one: $8 \times \frac{1}{8} = 1$. The volume of a parallelepiped with axes \mathbf{a}_1 , \mathbf{a}_2 , \mathbf{a}_3 is

$$V_c = |\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3|, \quad (3)$$

by elementary vector analysis. The basis associated with a primitive cell is called a primitive basis. No basis contains fewer atoms than a primitive basis contains. Another way of choosing a primitive cell is shown in Fig. 4. This is known to physicists as a **Wigner-Seitz cell**.

FUNDAMENTAL TYPES OF LATTICES

Crystal lattices can be carried or mapped into themselves by the lattice translations \mathbf{T} and by various other symmetry operations. A typical symmetry operation is that of rotation about an axis that passes through a lattice point. Lattices can be found such that one-, two-, three-, four-, and sixfold rotation axes carry the lattice into itself, corresponding to rotations by 2π , $2\pi/2$, $2\pi/3$, $2\pi/4$, and $2\pi/6$ radians and by integral multiples of these rotations. The rotation axes are denoted by the symbols 1, 2, 3, 4, and 6.

We cannot find a lattice that goes into itself under other rotations, such as by $2\pi/7$ radians or $2\pi/5$ radians. A single molecule properly designed can have any degree of rotational symmetry, but an infinite periodic lattice cannot. We can make a crystal from molecules that individually have a fivefold rotation axis, but we should not expect the lattice to have a fivefold rotation axis. In Fig. 5 we show what happens if we try to construct a periodic lattice having fivefold



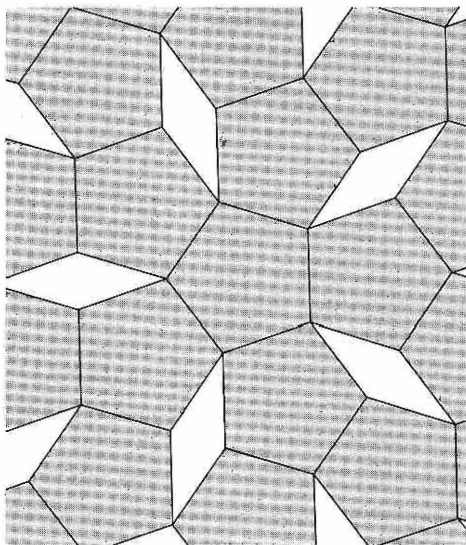



Figure 5 A fivefold axis of symmetry cannot exist in a periodic lattice because it is not possible to fill the area of a plane with a connected array of pentagons. We can, however, fill all the area of a plane with just two distinct designs of "tiles" or elementary polygons.




(a)




(b)



(c)

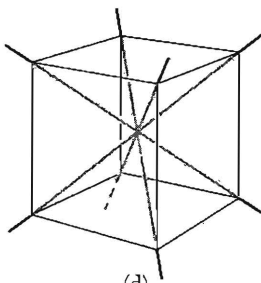

(d)

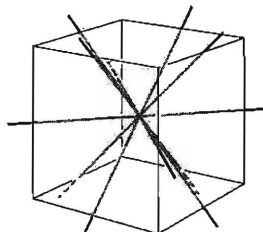

(e)

Figure 6 (a) A plane of symmetry parallel to the faces of a cube. (b) A diagonal plane of symmetry in a cube. (c) The three tetrad axes of a cube. (d) The four triad axes of a cube. (e) The six diad axes of a cube.

symmetry: the pentagons do not fit together to fill all space, showing that we cannot combine fivefold point symmetry with the required translational periodicity.

By lattice point group we mean the collection of symmetry operations which, applied about a lattice point, carry the lattice into itself. The possible rotations have been listed. We can have mirror reflections m about a plane through

a lattice point. The inversion operation is composed of a rotation of π followed by reflection in a plane normal to the rotation axis; the total effect is to replace \mathbf{r} by $-\mathbf{r}$. The symmetry axes and symmetry planes of a cube are shown in Fig. 6.

Two-Dimensional Lattice Types

The lattice in Fig. 3a was drawn for arbitrary \mathbf{a}_1 and \mathbf{a}_2 . A general lattice such as this is known as an **oblique lattice** and is invariant only under rotation of π and 2π about any lattice point. But special lattices of the oblique type can be invariant under rotation of $2\pi/3$, $2\pi/4$, or $2\pi/6$, or under mirror reflection. We must impose restrictive conditions on \mathbf{a}_1 and \mathbf{a}_2 if we want to construct a lattice that will be invariant under one or more of these new operations. There are four distinct types of restriction, and each leads to what we may call a **special lattice type**. Thus there are five distinct lattice types in two dimensions, the oblique lattice and the four special lattices shown in Fig. 7. **Bravais lattice** is the common phrase for a distinct lattice type; we say that there are five Bravais lattices in two dimensions.

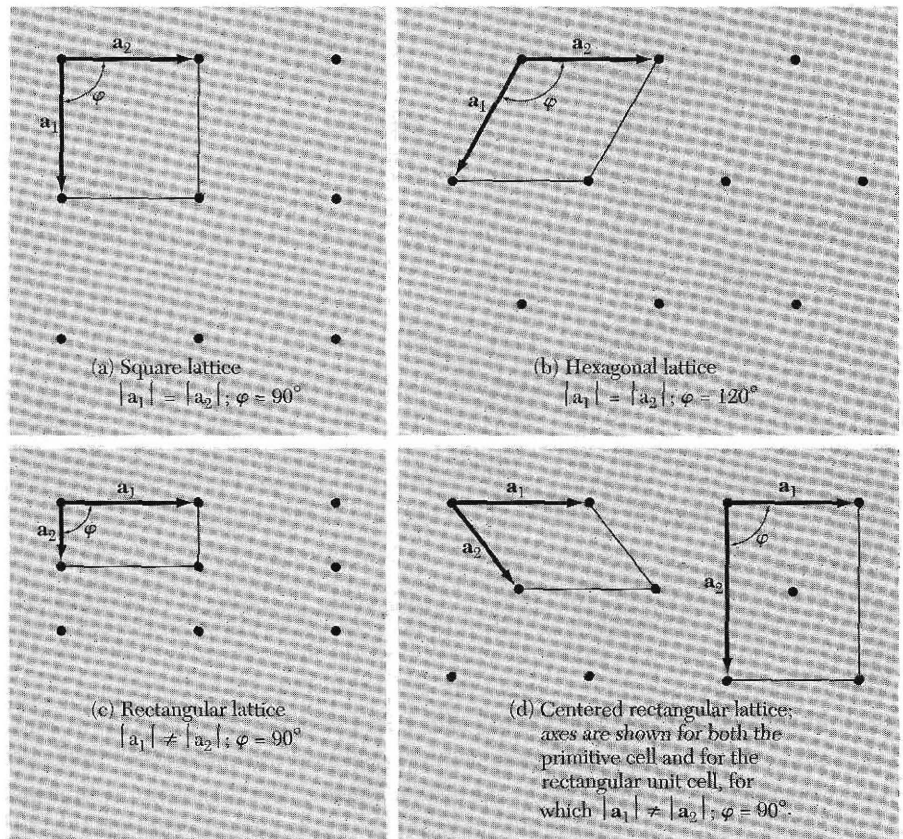


Figure 7 Four special lattices in two dimensions.

Three-Dimensional Lattice Types

The point symmetry groups in three dimensions require the 14 different lattice types listed in Table 1. The general lattice is triclinic, and there are 13 special lattices. These are grouped for convenience into systems classified according to seven types of cells, which are triclinic, monoclinic, orthorhombic, tetragonal, cubic, trigonal, and hexagonal. The division into systems is expressed in the table in terms of the axial relations that describe the cells. The cells in Fig. 8 are conventional cells: of these only the sc is a primitive cell. Often a nonprimitive cell has a more obvious relation with the point symmetry operations than has a primitive cell.

There are three lattices in the cubic system: the simple cubic (sc) lattice, the body-centered cubic (bcc) lattice, and the face-centered cubic (fcc) lattice.

Table 1 The 14 lattice types in three dimensions

System	Number of lattices	Restrictions on conventional cell axes and angles
Triclinic	1	$a_1 \neq a_2 \neq a_3$ $\alpha \neq \beta \neq \gamma$
Monoclinic	2	$a_1 \neq a_2 \neq a_3$ $\alpha = \gamma = 90^\circ \neq \beta$
Orthorhombic	4	$a_1 \neq a_2 \neq a_3$ $\alpha = \beta = \gamma = 90^\circ$
Tetragonal	2	$a_1 = a_2 \neq a_3$ $\alpha = \beta = \gamma = 90^\circ$
Cubic	3	$a_1 = a_2 = a_3$ $\alpha = \beta = \gamma = 90^\circ$
Trigonal	1	$a_1 = a_2 = a_3$ $\alpha = \beta = \gamma < 120^\circ, \neq 90^\circ$
Hexagonal	1	$a_1 = a_2 \neq a_3$ $\alpha = \beta = 90^\circ$ $\gamma = 120^\circ$

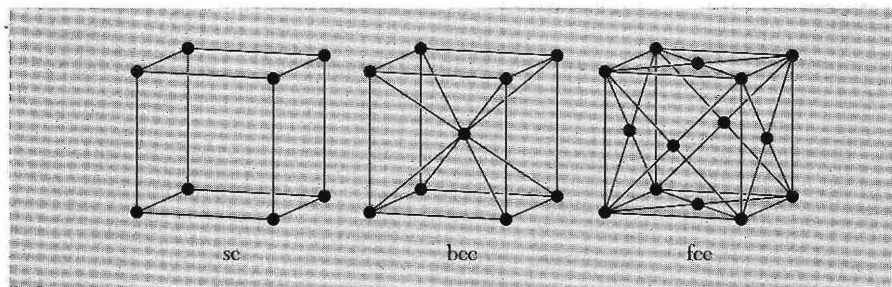


Figure 8 The cubic space lattices. The cells shown are the conventional cells.

Table 2 Characteristics of cubic lattices^a

	Simple	Body-centered	Face-centered
Volume, conventional cell	a^3	a^3	a^3
Lattice points per cell	1	2	4
Volume, primitive cell	a^3	$\frac{1}{2}a^3$	$\frac{1}{4}a^3$
Lattice points per unit volume	$1/a^3$	$2/a^3$	$4/a^3$
Number of nearest neighbors	6	8	12
Nearest-neighbor distance	a	$3^{1/2} a/2 = 0.866a$	$a/2^{1/2} = 0.707a$
Number of second neighbors	12	6	6
Second neighbor distance	$2^{1/2}a$	a	a
Packing fraction ^a	$\frac{1}{6}\pi$ =0.524	$\frac{1}{8}\pi\sqrt{3}$ =0.680	$\frac{1}{6}\pi\sqrt{2}$ =0.740

^aThe packing fraction is the maximum proportion of the available volume that can be filled with hard spheres.

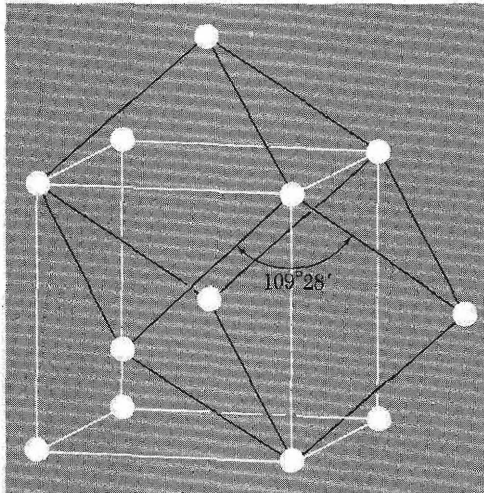


Figure 9 Body-centered cubic lattice, showing a primitive cell. The primitive cell shown is a rhombohedron of edge $\frac{1}{2}\sqrt{3}a$, and the angle between adjacent edges is $109^\circ28'$.

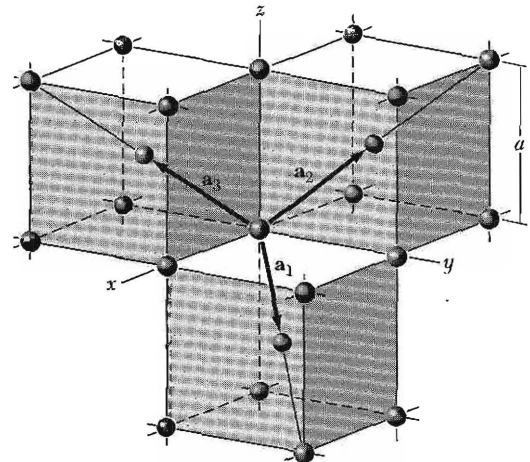


Figure 10 Primitive translation vectors of the body-centered cubic lattice; these vectors connect the lattice point at the origin to lattice points at the body centers. The primitive cell is obtained on completing the rhombohedron. In terms of the cube edge a , the primitive translation vectors are

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a(\hat{\mathbf{x}} + \hat{\mathbf{y}} - \hat{\mathbf{z}}) ; & \mathbf{a}_2 &= \frac{1}{2}a(-\hat{\mathbf{x}} + \hat{\mathbf{y}} + \hat{\mathbf{z}}) ; \\ \mathbf{a}_3 &= \frac{1}{2}a(\hat{\mathbf{x}} - \hat{\mathbf{y}} + \hat{\mathbf{z}}) . \end{aligned}$$

Here $\hat{\mathbf{x}}, \hat{\mathbf{y}}, \hat{\mathbf{z}}$ are the Cartesian unit vectors.

The characteristics of the three cubic lattices are summarized in Table 2. A primitive cell of the bcc lattice is shown in Fig. 9, and the primitive translation vectors are shown in Fig. 10. The primitive translation vectors of the fcc lattice are shown in Fig. 11. Primitive cells by definition contain only one lattice point, but the conventional bcc cell contains two lattice points, and the fcc cell contains four lattice points.

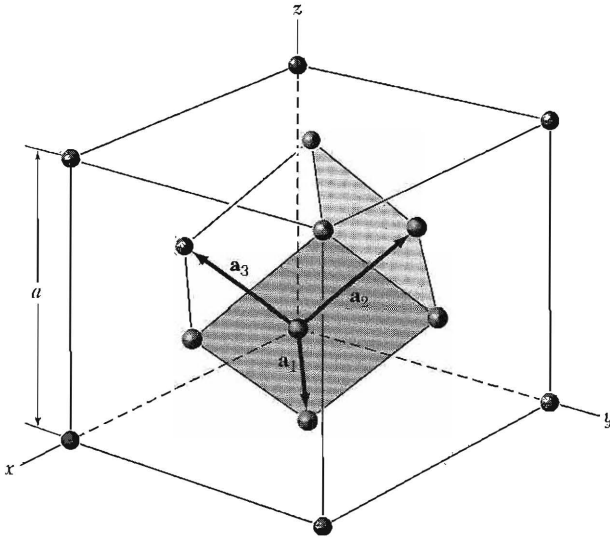


Figure 11 The rhombohedral primitive cell of the face-centered cubic crystal. The primitive translation vectors \mathbf{a}_1 , \mathbf{a}_2 , \mathbf{a}_3 connect the lattice point at the origin with lattice points at the face centers. As drawn, the primitive vectors are:

$$\mathbf{a}_1 = \frac{1}{2}a(\hat{x} + \hat{y}) ; \quad \mathbf{a}_2 = \frac{1}{2}a(\hat{y} + \hat{z}) ; \quad \mathbf{a}_3 = \frac{1}{2}a(\hat{z} + \hat{x}) .$$

The angles between the axes are 60° .

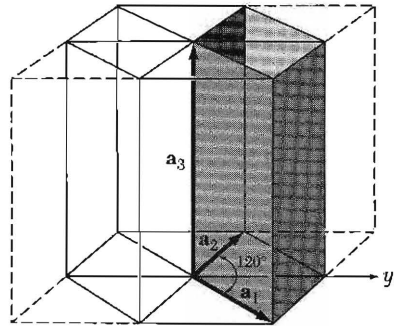


Figure 12 Relation of the primitive cell in the hexagonal system (heavy lines) to a prism of hexagonal symmetry. Here $a_1 = a_2 \neq a_3$.

The position of a point in a cell is specified by (2) in terms of the atomic coordinates x , y , z . Here each coordinate is a fraction of the axial length a_1 , a_2 , a_3 in the direction of the coordinate axis, with the origin taken at one corner of the cell. Thus the coordinates of the body center of a cell are $\frac{1}{2}\frac{1}{2}\frac{1}{2}$, and the face centers include $\frac{1}{2}\frac{1}{2}0$, $0\frac{1}{2}\frac{1}{2}$, $\frac{1}{2}0\frac{1}{2}$. In the hexagonal system the primitive cell is a right prism based on a rhombus with an included angle of 120° . Figure 12 shows the relationship of the rhombic cell to a hexagonal prism.

INDEX SYSTEM FOR CRYSTAL PLANES

The orientation of a crystal plane is determined by three points in the plane, provided they are not collinear. If each point lay on a different crystal axis, the plane could be specified by giving the coordinates of the points in terms of the lattice constants a_1 , a_2 , a_3 . However, it turns out to be more useful for structure analysis to specify the orientation of a plane by the indices determined by the following rules (Fig. 13).

- Find the intercepts on the axes in terms of the lattice constants a_1 , a_2 , a_3 . The axes may be those of a primitive or nonprimitive cell.

Figure 13 This plane intercepts the a_1 , a_2 , a_3 axes at $3a_1$, $2a_2$, $2a_3$. The reciprocals of these numbers are $\frac{1}{3}$, $\frac{1}{2}$, $\frac{1}{2}$. The smallest three integers having the same ratio are 2, 3, 3, and thus the indices of the plane are (233).

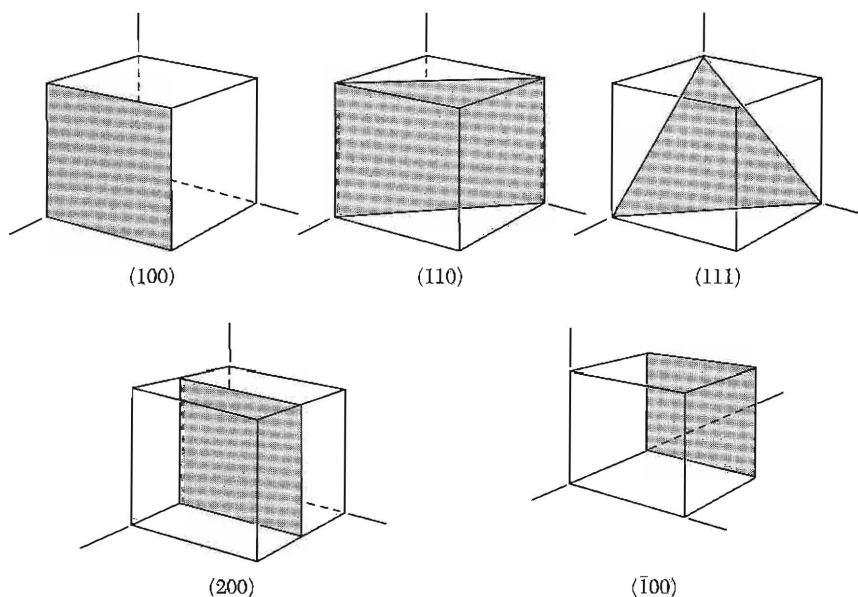
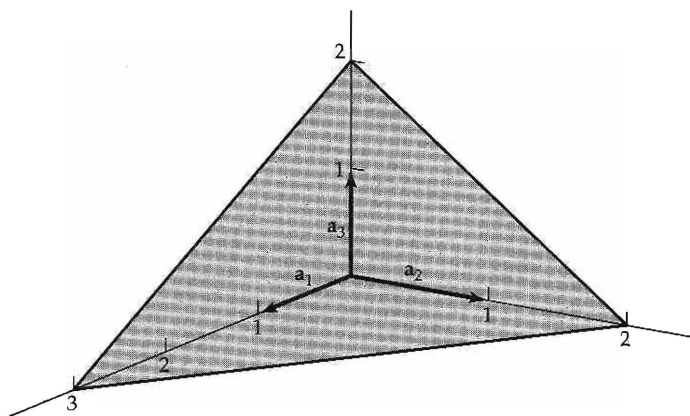


Figure 14 Indices of important planes in a cubic crystal. The plane (200) is parallel to (100) and to (100).

- Take the reciprocals of these numbers and then reduce to three integers having the same ratio, usually the smallest three integers. The result, enclosed in parentheses (hkl), is called the index of the plane.

For the plane whose intercepts are 4, 1, 2, the reciprocals are $\frac{1}{4}$, 1, and $\frac{1}{2}$; the smallest three integers having the same ratio are (142). For an intercept at infinity, the corresponding index is zero. The indices of some important planes in a cubic crystal are illustrated by Fig. 14. The indices (hkl) may denote a single plane or a set of parallel planes. If a plane cuts an axis on the negative side of the origin, the corresponding index is negative, indicated by placing a minus sign

above the index: $(h\bar{k}l)$. The cube faces of a cubic crystal are (100) , (010) , (001) , $(\bar{1}00)$, $(0\bar{1}0)$, and $(00\bar{1})$. Planes equivalent by symmetry may be denoted by curly brackets (braces) around indices; the set of cube faces is $\{100\}$. When we speak of the (200) plane we mean a plane parallel to (100) but cutting the \mathbf{a}_1 axis at $\frac{1}{2}a$.

The indices $[uvw]$ of a direction in a crystal are the set of the smallest integers that have the ratio of the components of a vector in the desired direction, referred to the axes. The \mathbf{a}_1 axis is the $[100]$ direction; the $-\mathbf{a}_2$ axis is the $[0\bar{1}0]$ direction. In cubic crystals the direction $[hkl]$ is perpendicular to a plane (hkl) having the same indices, but this is not generally true in other crystal systems.

SIMPLE CRYSTAL STRUCTURES

We discuss simple crystal structures of general interest: the sodium chloride, cesium chloride, hexagonal close-packed, diamond, and cubic zinc sulfide structures.

Sodium Chloride Structure

The sodium chloride, NaCl , structure is shown in Figs. 15 and 16. The lattice is face-centered cubic; the basis consists of one Na^+ ion and one Cl^- ion

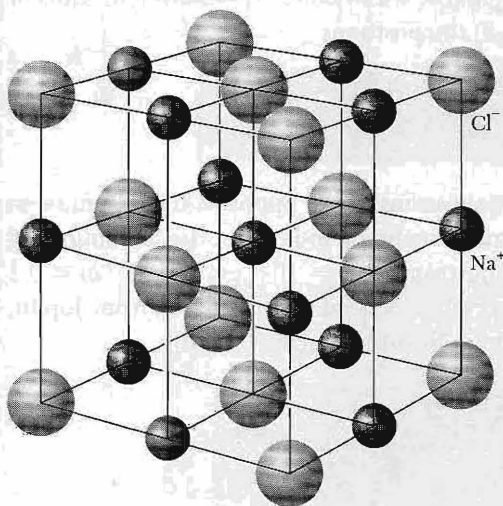


Figure 15 We may construct the sodium chloride crystal structure by arranging Na^+ and Cl^- ions alternately at the lattice points of a simple cubic lattice. In the crystal each ion is surrounded by six nearest neighbors of the opposite charge. The space lattice is fcc, and the basis has one Cl^- ion at 000 and one Na^+ ion at $\frac{1}{2}\frac{1}{2}\frac{1}{2}$. The figure shows one conventional cubic cell. The ionic diameters here are reduced in relation to the cell in order to clarify the spatial arrangement.

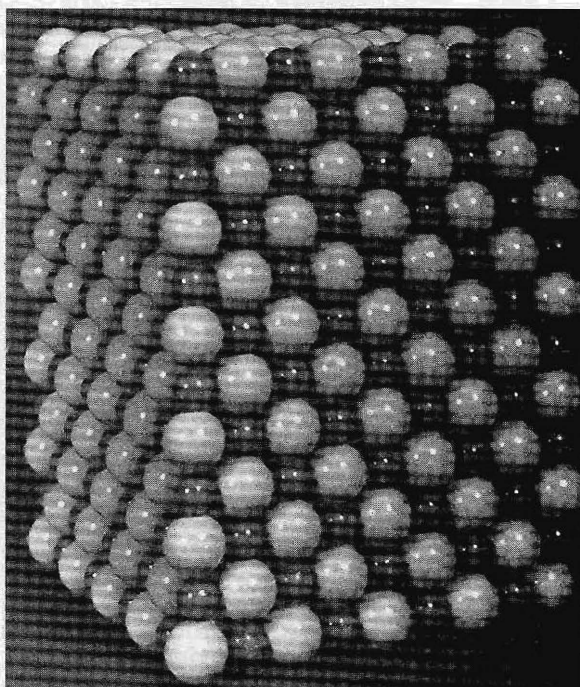


Figure 16 Model of sodium chloride. The sodium ions are smaller than the chlorine ions. (Courtesy of A. N. Holden and P. Singer.)

2

Wave Diffraction and the Reciprocal Lattice

DIFFRACTION OF WAVES BY CRYSTALS	25
The Bragg law	25
SCATTERED WAVE AMPLITUDE	26
Fourier analysis	27
Reciprocal lattice vectors	29
Diffraction conditions	30
Laue equations	33
BRILLOUIN ZONES	32
Reciprocal lattice to sc lattice	34
Reciprocal lattice to bcc lattice	36
Reciprocal lattice to fcc lattice	37
FOURIER ANALYSIS OF THE BASIS	39
Structure factor of the bcc lattice	40
Structure factor of the fcc lattice	40
Atomic form factor	41
SUMMARY	43
PROBLEMS	43
1. Interplanar separation	43
2. Hexagonal space lattice	44
3. Volume of Brillouin zone	44
4. Width of diffraction maximum	44
5. Structure factor of diamond	45
6. Form factor of atomic hydrogen	45
7. Diatomic line	45

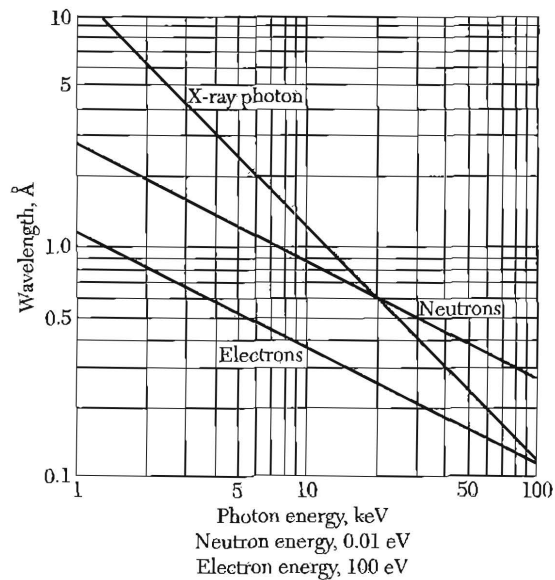


Figure 1 Wavelength versus particle energy, for photons, neutrons, and electrons.

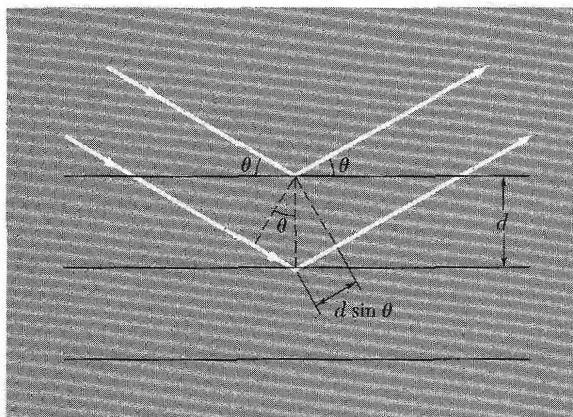


Figure 2 Derivation of the Bragg equation $2d \sin \theta = n\lambda$; here d is the spacing of parallel atomic planes and 2π is the difference in phase between reflections from successive planes. The reflecting planes have nothing to do with the surface planes bounding the particular specimen.

CHAPTER 2: WAVE DIFFRACTION AND THE RECIPROCAL LATTICE

DIFFRACTION OF WAVES BY CRYSTALS

The Bragg law

We study crystal structure through the diffraction of photons, neutrons, and electrons (Fig. 1). The diffraction depends on the crystal structure and on the wavelength. At optical wavelengths such as 5000 Å, the superposition of the waves scattered elastically by the individual atoms of a crystal results in ordinary optical refraction. When the wavelength of the radiation is comparable with or smaller than the lattice constant, we may find diffracted beams in directions quite different from the incident direction.

W. L. Bragg presented a simple explanation of the diffracted beams from a crystal. The Bragg derivation is simple but is convincing only because it reproduces the correct result. Suppose that the incident waves are reflected specularly from parallel planes of atoms in the crystal, with each plane reflecting only a very small fraction of the radiation, like a lightly silvered mirror. In specular (mirrorlike) reflection the angle of incidence is equal to the angle of reflection. The diffracted beams are found when the reflections from parallel planes of atoms interfere constructively, as in Fig. 2. We treat elastic scattering, in which the energy of the x-ray is not changed on reflection.

Consider parallel lattice planes spaced d apart. The radiation is incident in the plane of the paper. The path difference for rays reflected from adjacent planes is $2d \sin \theta$, where θ is measured from the plane. Constructive interference of the radiation from successive planes occurs when the path difference is an integral number n of wavelengths λ , so that

$$2d \sin \theta = n\lambda \quad (1)$$

This is the Bragg law, which can be satisfied only for wavelength $\lambda \leq 2d$.

Although the reflection from each plane is specular, for only certain values of θ will the reflections from all periodic parallel planes add up in phase to give a strong reflected beam. If each plane were perfectly reflecting, only the first plane of a parallel set would see the radiation, and any wavelength would be reflected. But each plane reflects 10^{-3} to 10^{-5} of the incident radiation, so that 10^3 to 10^5 planes may contribute to the formation of the Bragg-reflected beam in a perfect crystal. Reflection by a single plane of atoms is treated in Chapter 17 on surface physics.

The Bragg law is a consequence of the periodicity of the lattice. Notice that the law does not refer to the composition of the basis of atoms associated

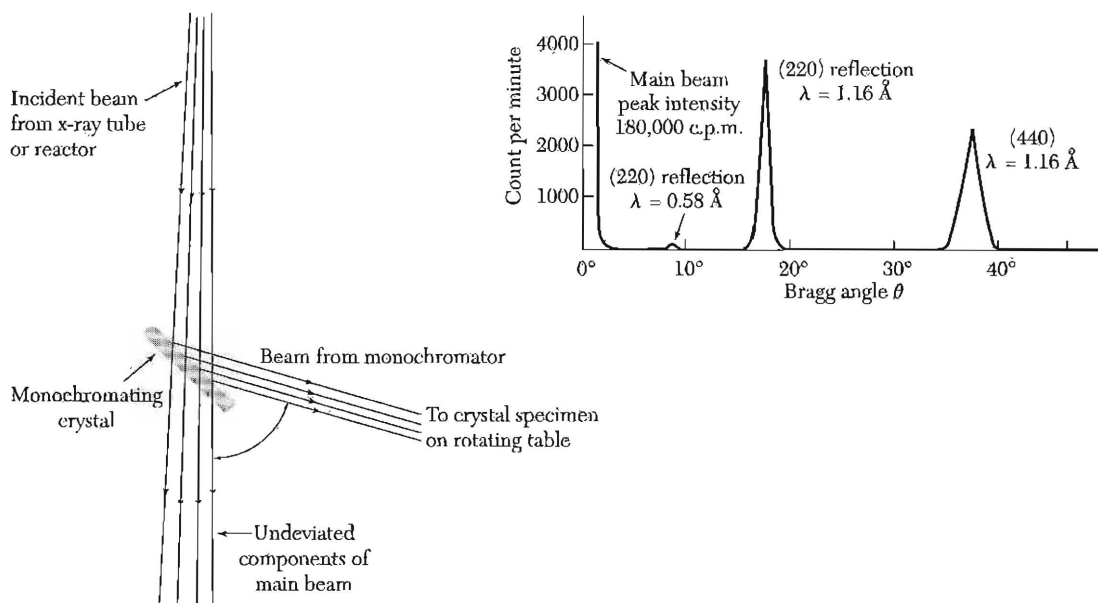


Figure 3 Sketch of a monochromator which by Bragg reflection selects a narrow spectrum of x-ray or neutron wavelengths from a broad spectrum incident beam. The upper part of the figure shows the analysis (obtained by reflection from a second crystal) of the purity of a 1.16 Å beam of neutrons from a calcium fluoride crystal monochromator. (After G. Bacon.)

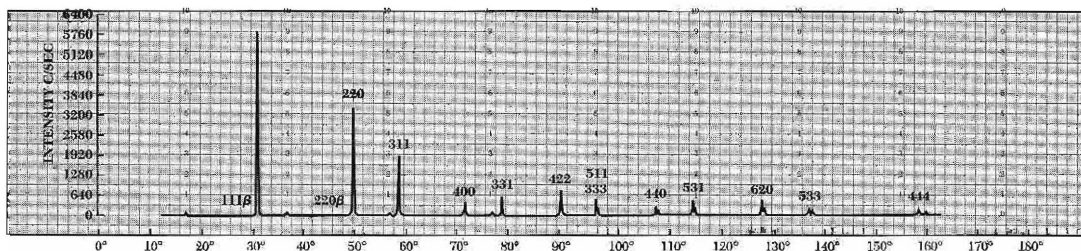


Figure 4 X-ray diffractometer recording of powdered silicon, showing a counter recording of the diffracted beams. (Courtesy of W. Parrish.)

with every lattice point. We shall see, however, that the composition of the basis determines the relative intensity of the various orders of diffraction (denoted by n above) from a given set of parallel planes. Bragg reflection from a single crystal is shown in Fig. 3 and from a powder in Fig. 4.

SCATTERED WAVE AMPLITUDE

The Bragg derivation of the diffraction condition (1) gives a neat statement of the condition for the constructive interference of waves scattered from the lattice points. We need a deeper analysis to determine the scattering

intensity from the basis of atoms, which means from the spatial distribution of electrons within each cell.

Fourier Analysis

We have seen that a crystal is invariant under any translation of the form $\mathbf{T} = u_1\mathbf{a}_1 + u_2\mathbf{a}_2 + u_3\mathbf{a}_3$, where u_1, u_2, u_3 are integers and $\mathbf{a}_1, \mathbf{a}_2, \mathbf{a}_3$ are the crystal axes. Any local physical property of the crystal, such as the charge concentration, electron number density, or magnetic moment density is invariant under \mathbf{T} . What is most important to us here is that the electron number density $n(\mathbf{r})$ is a periodic function of \mathbf{r} , with periods $\mathbf{a}_1, \mathbf{a}_2, \mathbf{a}_3$ in the directions of the three crystal axes, respectively. Thus

$$n(\mathbf{r} + \mathbf{T}) = n(\mathbf{r}) . \quad (2)$$

Such periodicity creates an ideal situation for Fourier analysis. The most interesting properties of crystals are directly related to the Fourier components of the electron density.

We consider first a function $n(x)$ in one dimension with period a in the direction x . We expand $n(x)$ in a Fourier series of sines and cosines:

$$n(x) = n_0 + \sum_{p>0} [C_p \cos(2\pi p x/a) + S_p \sin(2\pi p x/a)] , \quad (3)$$

where the p are positive integers and C_p, S_p are real constants, called the Fourier coefficients of the expansion. The factor $2\pi/a$ in the arguments ensures that $n(x)$ has the period a :

$$\begin{aligned} n(x+a) &= n_0 + \sum [C_p \cos(2\pi p x/a + 2\pi p) + S_p \sin(2\pi p x/a + 2\pi p)] \\ &= n_0 + \sum [C_p \cos(2\pi p x/a) + S_p \sin(2\pi p x/a)] = n(x) . \end{aligned} \quad (4)$$

We say that $2\pi p/a$ is a point in the reciprocal lattice or Fourier space of the crystal. In one dimension these points lie on a line. The **reciprocal lattice points** tell us the allowed terms in the Fourier series (4) or (5). A term is allowed if it is consistent with the periodicity of the crystal, as in Fig. 5; other

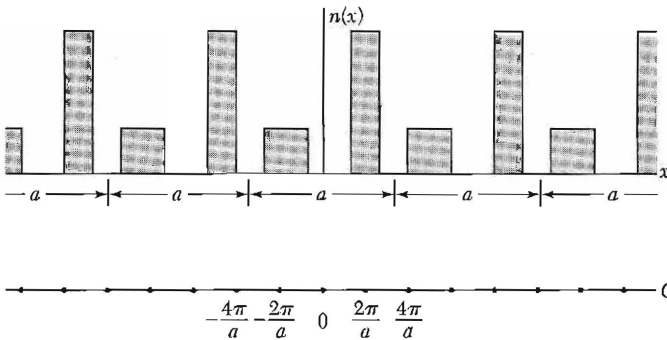


Figure 5
period a .
may appear
 $n(x) = \sum$

points in the reciprocal space are not allowed in the Fourier expansion of a periodic function.

It is convenient to write the series (4) in the compact form

$$n(x) = \sum_p n_p \exp(i2\pi p x/a) , \quad (5)$$

where the sum is over all integers p : positive, negative, and zero. The coefficients n_p now are complex numbers. To ensure that $n(x)$ is a real function, we require

$$n_{-p}^* = n_p , \quad (6)$$

for then the sum of the terms in p and $-p$ is real. The asterisk on n_{-p}^* denotes the complex conjugate of n_{-p} .

With $\varphi = 2\pi p x/a$, the sum of the terms in p and $-p$ in (5) is real if (6) is satisfied. The sum is

$$\begin{aligned} n_p(\cos \varphi + i \sin \varphi) + n_{-p}(\cos \varphi - i \sin \varphi) \\ = (n_p + n_{-p})\cos \varphi + i(n_p - n_{-p})\sin \varphi , \end{aligned} \quad (7)$$

which in turn is equal to the real function

$$2\text{Re}\{n_p\} \cos \varphi - 2\text{Im}\{n_p\} \sin \varphi \quad (8)$$

if (6) is satisfied. Here $\text{Re}\{n_p\}$ and $\text{Im}\{n_p\}$ are real and denote the real and imaginary parts of n_p . Thus the number density $n(x)$ is a real function, as desired.

The extension of the Fourier analysis to periodic functions $n(\mathbf{r})$ in three dimensions is straightforward. We must find a set of vectors \mathbf{G} such that

$$n(\mathbf{r}) = \sum_{\mathbf{G}} n_{\mathbf{G}} \exp(i\mathbf{G} \cdot \mathbf{r}) \quad (9)$$

is invariant under all crystal translations \mathbf{T} that leave the crystal invariant. It will be shown below that the set of Fourier coefficients $n_{\mathbf{G}}$ determines the x-ray scattering amplitude.

Inversion of Fourier Series. We now show that the Fourier coefficient n_p in the series (5) is given by

$$n_p = a^{-1} \int_0^a dx n(x) \exp(-i2\pi p x/a) . \quad (10)$$

Substitute (5) in (10) to obtain

$$n_p = a^{-1} \sum_{p'} n_{p'} \int_0^a dx \exp[i2\pi(p' - p)x/a] . \quad (11)$$

If $p' \neq p$ the value of the integral is

$$\frac{a}{i2\pi(p' - p)} (e^{i2\pi(p' - p)} - 1) = 0 ,$$

because $p' - p$ is an integer and $\exp[i2\pi(\text{integer})] = 1$. For the term $p' = p$ the integrand is $\exp(i0) = 1$, and the value of the integral is a , so that $n_p = a^{-1}n_p a = n_p$, which is an identity, so that (10) is an identity.

As in (10), the inversion of (9) gives

$$n_{\mathbf{G}} = V_c^{-1} \int_{\text{cell}} dV n(\mathbf{r}) \exp(-i\mathbf{G} \cdot \mathbf{r}) . \quad (12)$$

Here V_c is the volume of a cell of the crystal.

Reciprocal Lattice Vectors

To proceed further with the Fourier analysis of the electron concentration we must find the vectors \mathbf{G} of the Fourier sum $\sum n_{\mathbf{G}} \exp(i\mathbf{G} \cdot \mathbf{r})$ as in (9). There is a powerful, somewhat abstract procedure for doing this. The procedure forms the theoretical basis for much of solid state physics, where Fourier analysis is the order of the day.

We construct the axis vectors $\mathbf{b}_1, \mathbf{b}_2, \mathbf{b}_3$ of the **reciprocal lattice**:

$$\mathbf{b}_1 = 2\pi \frac{\mathbf{a}_2 \times \mathbf{a}_3}{\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3} ; \quad \mathbf{b}_2 = 2\pi \frac{\mathbf{a}_3 \times \mathbf{a}_1}{\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3} ; \quad \mathbf{b}_3 = 2\pi \frac{\mathbf{a}_1 \times \mathbf{a}_2}{\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3} . \quad (13)$$

The factors 2π are not used by crystallographers but are convenient in solid state physics.

If $\mathbf{a}_1, \mathbf{a}_2, \mathbf{a}_3$ are primitive vectors of the crystal lattice, then $\mathbf{b}_1, \mathbf{b}_2, \mathbf{b}_3$ are **primitive vectors of the reciprocal lattice**. Each vector defined by (13) is orthogonal to two axis vectors of the crystal lattice. Thus $\mathbf{b}_1, \mathbf{b}_2, \mathbf{b}_3$ have the property

$$\mathbf{b}_i \cdot \mathbf{a}_j = 2\pi \delta_{ij} , \quad (14)$$

where $\delta_{ij} = 1$ if $i = j$ and $\delta_{ij} = 0$ if $i \neq j$.

Points in the reciprocal lattice are mapped by the set of vectors

$$\mathbf{G} = v_1 \mathbf{b}_1 + v_2 \mathbf{b}_2 + v_3 \mathbf{b}_3 , \quad (15)$$

where v_1, v_2, v_3 are integers. A vector \mathbf{G} of this form is a **reciprocal lattice** vector.

The vectors \mathbf{G} in the Fourier series (9) are just the reciprocal lattice vectors (15), for then the Fourier series representation of the electron density has the desired invariance under any crystal translation $\mathbf{T} = u_1 \mathbf{a}_1 + u_2 \mathbf{a}_2 + u_3 \mathbf{a}_3$. From (9),

$$n(\mathbf{r} + \mathbf{T}) = \sum_{\mathbf{G}} n_{\mathbf{G}} \exp(i\mathbf{G} \cdot \mathbf{r}) \exp(i\mathbf{G} \cdot \mathbf{T}) . \quad (16)$$

But $\exp(i\mathbf{G} \cdot \mathbf{T}) = 1$, because

$$\begin{aligned}\exp(i\mathbf{G} \cdot \mathbf{T}) &= \exp[i(v_1\mathbf{b}_1 + v_2\mathbf{b}_2 + v_3\mathbf{b}_3) \cdot (u_1\mathbf{a}_1 + u_2\mathbf{a}_2 + u_3\mathbf{a}_3)] \\ &= \exp[i2\pi(v_1u_1 + v_2u_2 + v_3u_3)] .\end{aligned}\quad (17)$$

The argument of the exponential has the form $2\pi i$ times an integer, because $v_1u_1 + v_2u_2 + v_3u_3$ is an integer, being the sum of products of integers. Thus by (9) we have the desired invariance, $n(\mathbf{r} + \mathbf{T}) = n(\mathbf{r}) = \sum n_{\mathbf{G}} \exp(i\mathbf{G} \cdot \mathbf{r})$.

Every crystal structure has two lattices associated with it, the crystal lattice and the reciprocal lattice. A diffraction pattern of a crystal is, as we shall show, a map of the reciprocal lattice of the crystal. A microscope image, if it could be resolved on a fine enough scale, is a map of the crystal structure in real space. The two lattices are related by the definitions (13). Thus when we rotate a crystal in a holder, we rotate both the direct lattice and the reciprocal lattice.

Vectors in the direct lattice have the dimensions of [length]; vectors in the reciprocal lattice have the dimensions of [1/length]. The reciprocal lattice is a lattice in the Fourier space associated with the crystal. The term is motivated below. Wavevectors are always drawn in Fourier space, so that every position in Fourier space may have a meaning as a description of a wave, but there is a special significance to the points defined by the set of \mathbf{G} 's associated with a crystal structure.

Diffraction Conditions

Theorem. The set of reciprocal lattice vectors \mathbf{G} determines the possible x-ray reflections.

We see in Fig. 6 that the difference in phase factors is $\exp[i(\mathbf{k} - \mathbf{k}') \cdot \mathbf{r}]$ between beams scattered from volume elements \mathbf{r} apart. The wavevectors of the incoming and outgoing beams are \mathbf{k} and \mathbf{k}' . We suppose that the amplitude

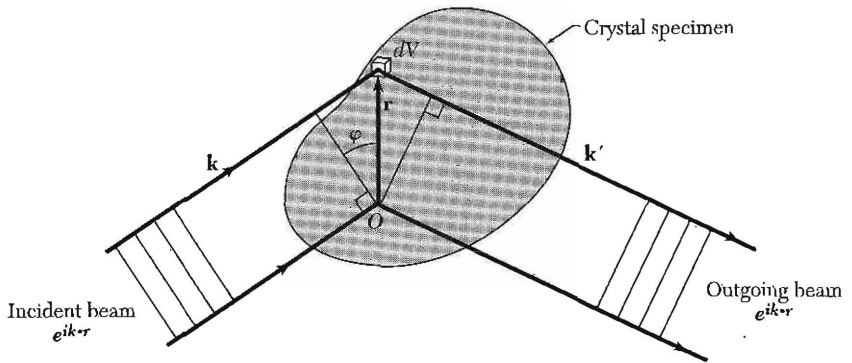


Figure 6 The difference in path length of the incident wave \mathbf{k} at the points O , \mathbf{r} is $r \sin \varphi$, and the difference in phase angle is $(2\pi r \sin \varphi)/\lambda$, which is equal to $\mathbf{k} \cdot \mathbf{r}$. For the diffracted wave the difference in phase angle is $-\mathbf{k}' \cdot \mathbf{r}$. The total difference in phase angle is $(\mathbf{k} - \mathbf{k}') \cdot \mathbf{r}$, and the wave scattered from dV at \mathbf{r} has the phase factor $\exp[i(\mathbf{k} - \mathbf{k}') \cdot \mathbf{r}]$ relative to the wave scattered from a volume element at the origin O .

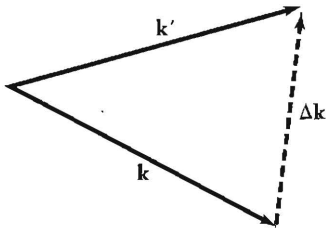


Figure 7 Definition of the scattering vector $\Delta\mathbf{k}$ such that $\mathbf{k} + \Delta\mathbf{k} = \mathbf{k}'$. In elastic scattering the magnitudes satisfy $k' = k$. Further, in Bragg scattering from a periodic lattice, any allowed $\Delta\mathbf{k}$ must equal some reciprocal lattice vector \mathbf{G} .

of the wave scattered from a volume element is proportional to the local electron concentration $n(\mathbf{r})$. The total amplitude of the scattered wave in the direction of \mathbf{k}' is proportional to the integral over the crystal of $n(\mathbf{r}) dV$ times the phase factor $\exp[i(\mathbf{k} - \mathbf{k}') \cdot \mathbf{r}]$.

In other words, the amplitude of the electric or magnetic field vectors in the scattered electromagnetic wave is proportional to the following integral which defines the quantity F that we call the **scattering amplitude**:

$$F = \int dV n(\mathbf{r}) \exp[i(\mathbf{k} - \mathbf{k}') \cdot \mathbf{r}] = \int dV n(\mathbf{r}) \exp(-i\Delta\mathbf{k} \cdot \mathbf{r}) , \quad (18)$$

where $\mathbf{k} - \mathbf{k}' = -\Delta\mathbf{k}$, or

$$\mathbf{k} + \Delta\mathbf{k} = \mathbf{k}' . \quad (19)$$

Here $\Delta\mathbf{k}$ measures the change in wavevector and is called the **scattering vector** (Fig. 7). We add $\Delta\mathbf{k}$ to \mathbf{k} to obtain \mathbf{k}' , the wavevector of the scattered beam.

We introduce into (18) the Fourier components (9) of $n(\mathbf{r})$ to obtain for the scattering amplitude

$$F = \sum_{\mathbf{G}} \int dV n_{\mathbf{G}} \exp[i(\mathbf{G} - \Delta\mathbf{k}) \cdot \mathbf{r}] . \quad (20)$$

When the scattering vector $\Delta\mathbf{k}$ is equal to a particular reciprocal lattice vector,

$$\Delta\mathbf{k} = \mathbf{G} , \quad (21)$$

the argument of the exponential vanishes and $F = Vn_{\mathbf{G}}$. It is a simple exercise (Problem 4) to show that F is negligibly small when $\Delta\mathbf{k}$ differs significantly from any reciprocal lattice vector.

In elastic scattering of a photon its energy $\hbar\omega$ is conserved, so that the frequency $\omega' = ck'$ of the emergent beam is equal to the frequency of the incident beam. Thus the magnitudes k and k' are equal, and $k^2 = k'^2$, a result that holds also for elastic scattering of electron and neutron beams. From (21) we found $\Delta\mathbf{k} = \mathbf{G}$ or $\mathbf{k} + \mathbf{G} = \mathbf{k}'$, so that the **diffraction condition** is written as $(\mathbf{k} + \mathbf{G})^2 = k^2$, or

$$2\mathbf{k} \cdot \mathbf{G} + G^2 = 0 . \quad (22)$$

This is the central result of the theory of elastic scattering of waves in a periodic lattice. If \mathbf{G} is a reciprocal lattice vector, so is $-\mathbf{G}$, and with this substitution we can write (22) as

$$2\mathbf{k} \cdot \mathbf{G} = G^2 \quad (23)$$

This particular expression is often used as the condition for diffraction.

Equation (23) is another statement of the Bragg condition (1). The result of Problem 1 is that the spacing $d(hkl)$ between parallel lattice planes that are normal to the direction $\mathbf{G} = h\mathbf{b}_1 + k\mathbf{b}_2 + l\mathbf{b}_3$ is $d(hkl) = 2\pi/|\mathbf{G}|$. Thus the result $2\mathbf{k} \cdot \mathbf{G} = G^2$ may be written as

$$2(2\pi/\lambda) \sin \theta = 2\pi/d(hkl) \quad ,$$

or $2d(hkl) \sin \theta = \lambda$. Here θ is the angle between the incident beam and the crystal plane.

The integers hkl that define \mathbf{G} are not necessarily identical with the indices of an actual crystal plane, because the hkl may contain a common factor n , whereas in the definition of the indices in Chapter 1 the common factor has been eliminated. We thus obtain the Bragg result:

$$2d \sin \theta = n\lambda \quad , \quad (24)$$

where d is the spacing between adjacent parallel planes with indices h/n , k/n , l/n .

Laue Equations

The original result (21) of diffraction theory, namely that $\Delta\mathbf{k} = \mathbf{G}$, may be expressed in another way to give what are called the Laue equations. These are valuable because of their geometrical representation. Take the scalar product of both $\Delta\mathbf{k}$ and \mathbf{G} successively with \mathbf{a}_1 , \mathbf{a}_2 , \mathbf{a}_3 . From (14) and (15) we get

$$\mathbf{a}_1 \cdot \Delta\mathbf{k} = 2\pi v_1 \quad ; \quad \mathbf{a}_2 \cdot \Delta\mathbf{k} = 2\pi v_2 \quad ; \quad \mathbf{a}_3 \cdot \Delta\mathbf{k} = 2\pi v_3 \quad . \quad (25)$$

These equations have a simple geometrical interpretation. The first equation $\mathbf{a}_1 \cdot \Delta\mathbf{k} = 2\pi v_1$ tells us that $\Delta\mathbf{k}$ lies on a certain cone about the direction of \mathbf{a}_1 . The second equation tells us that $\Delta\mathbf{k}$ lies on a cone about \mathbf{a}_2 as well, and the third equation requires that $\Delta\mathbf{k}$ lies on a cone about \mathbf{a}_3 . Thus, at a reflection $\Delta\mathbf{k}$ must satisfy all three equations; it must lie at the common line of intersection of *three* cones, which is a severe condition that can be satisfied only by systematic sweeping or searching in wavelength or crystal orientation—or by sheer accident.

A beautiful construction, the Ewald construction, is exhibited in Fig. 8. This helps us visualize the nature of the accident that must occur in order to satisfy the diffraction condition in three dimensions.

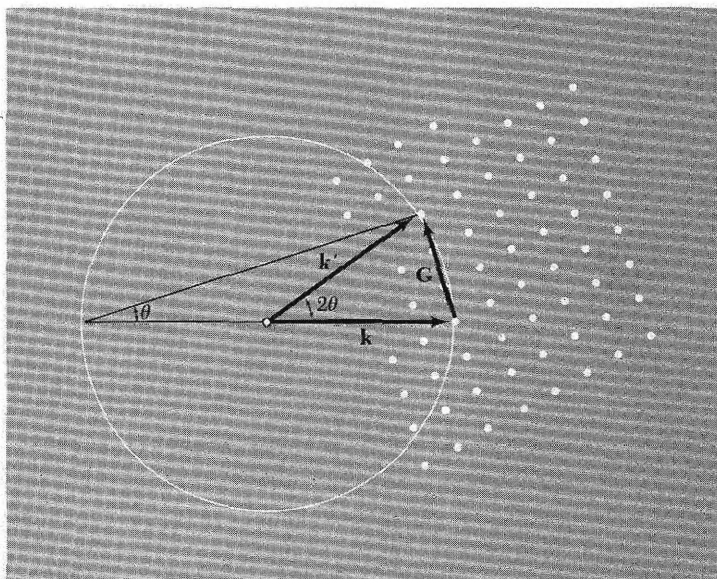


Figure 8 The points on the right-hand side are reciprocal-lattice points of the crystal. The vector \mathbf{k} is drawn in the direction of the incident x-ray beam, and the origin is chosen such that \mathbf{k} terminates at any reciprocal lattice point. We draw a sphere of radius $k = 2\pi/\lambda$ about the origin of \mathbf{k} . A diffracted beam will be formed if this sphere intersects any other point in the reciprocal lattice. The sphere as drawn intercepts a point connected with the end of \mathbf{k} by a reciprocal lattice vector \mathbf{G} . The diffracted x-ray beam is in the direction $\mathbf{k}' = \mathbf{k} + \mathbf{G}$. The angle θ is the Bragg angle of Fig. 2. This construction is due to P. P. Ewald.

BRILLOUIN ZONES

Brillouin gave the statement of the diffraction condition that is most widely used in solid state physics, which means in the description of electron energy band theory and of the elementary excitations of other kinds. A Brillouin zone is defined as a Wigner-Seitz primitive cell in the reciprocal lattice. (The construction in the direct lattice was shown in Fig. 1.4.) The Brillouin zone gives a vivid geometrical interpretation of the diffraction condition $2\mathbf{k} \cdot \mathbf{G} = G^2$ of Eq. (23). We divide both sides by 4 to obtain

$$\mathbf{k} \cdot \left(\frac{1}{2}\mathbf{G}\right) = \left(\frac{1}{2}G\right)^2. \quad (26)$$

We now work in reciprocal space, the space of the \mathbf{k} 's and \mathbf{G} 's. Select a vector \mathbf{G} from the origin to a reciprocal lattice point. Construct a plane normal to this vector \mathbf{G} at its midpoint. This plane forms a part of a zone boundary (Fig. 9a). An x-ray beam in the crystal will be diffracted if its wavevector \mathbf{k} has the magnitude and direction required by (26). The diffracted beam will then be in the direction $\mathbf{k} - \mathbf{G}$, as we see from (19) with $\Delta\mathbf{k} = -\mathbf{G}$. Thus the Brillouin construction exhibits all the wavevectors \mathbf{k} which can be Bragg-reflected by the crystal.

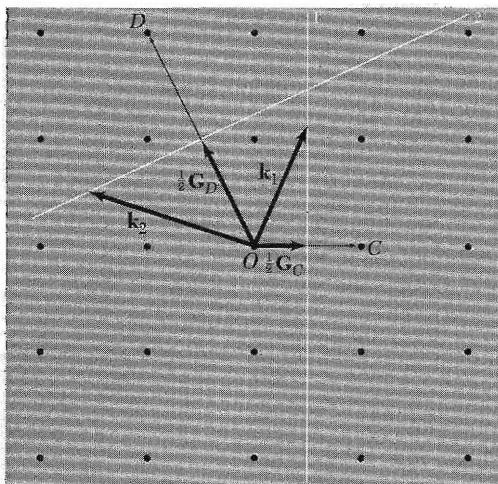


Figure 9a Reciprocal lattice points near the point O at the origin of the reciprocal lattice. The reciprocal lattice vector \mathbf{G}_C connects points OC ; and \mathbf{G}_D connects OD . Two planes 1 and 2 are drawn which are the perpendicular bisectors of \mathbf{G}_C and \mathbf{G}_D , respectively. Any vector from the origin to the plane 1, such as \mathbf{k}_1 , will satisfy the diffraction condition $\mathbf{k}_1 \cdot (\frac{1}{2} \mathbf{G}_C) = (\frac{1}{2} \mathbf{G}_C)^2$. Any vector from the origin to the plane 2, such as \mathbf{k}_2 , will satisfy the diffraction condition $\mathbf{k}_2 \cdot (\frac{1}{2} \mathbf{G}_D) = (\frac{1}{2} \mathbf{G}_D)^2$.

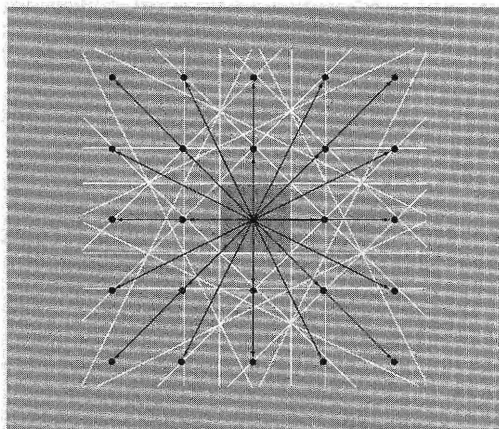


Figure 9b Square reciprocal lattice with reciprocal lattice vectors shown as fine black lines. The lines shown in white are perpendicular bisectors of the reciprocal lattice vectors. The central square is the smallest volume about the origin which is bounded entirely by white lines. The square is the Wigner-Seitz primitive cell of the reciprocal lattice. It is called the first Brillouin zone.

The set of planes that are the perpendicular bisectors of the reciprocal lattice vectors is of general importance in the theory of wave propagation in crystals: A wave whose wavevector drawn from the origin terminates on any of these planes will satisfy the condition for diffraction. These planes divide the Fourier space of the crystal into fragments, as shown in Fig. 9b for a square lattice. The central square is a primitive cell of the reciprocal lattice. It is a Wigner-Seitz cell of the reciprocal lattice.

The central cell in the reciprocal lattice is of special importance in the theory of solids, and we call it the first Brillouin zone. *The first Brillouin zone is the smallest volume entirely enclosed by planes that are the perpendicular bisectors of the reciprocal lattice vectors drawn from the origin.* Examples are shown in Figs. 10 and 11.

Historically, Brillouin zones are not part of the language of x-ray diffraction analysis of crystal structures, but the zones are an essential part of the analysis of the electronic energy-band structure of crystals.

Reciprocal Lattice to sc Lattice

The primitive translation vectors of a simple cubic lattice may be taken as the set

$$\mathbf{a}_1 = a\hat{\mathbf{x}} ; \quad \mathbf{a}_2 = a\hat{\mathbf{y}} ; \quad \mathbf{a}_3 = a\hat{\mathbf{z}} . \quad (27a)$$

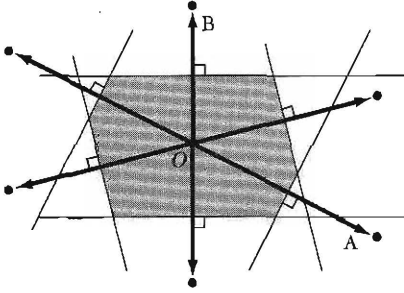


Figure 10 Construction of the first Brillouin zone for an oblique lattice in two dimensions. We first draw a number of vectors from O to nearby points in the reciprocal lattice. Next we construct lines perpendicular to these vectors at their mid-points. The smallest enclosed area is the first Brillouin zone.

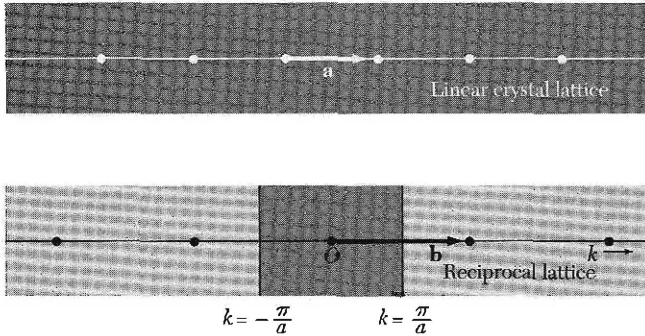


Figure 11 Crystal and reciprocal lattices in one dimension. The basis vector in the reciprocal lattice is \mathbf{b} , of length equal to $2\pi/a$. The shortest reciprocal lattice vectors from the origin are \mathbf{b} and $-\mathbf{b}$. The perpendicular bisectors of these vectors form the boundaries of the first Brillouin zone. The boundaries are at $k = \pm\pi/a$.

Here $\hat{\mathbf{x}}, \hat{\mathbf{y}}, \hat{\mathbf{z}}$ are orthogonal vectors of unit length. The volume of the cell is $\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3 = a^3$. The primitive translation vectors of the reciprocal lattice are found from the standard prescription (13):

$$\mathbf{b}_1 = (2\pi/a)\hat{\mathbf{x}} ; \quad \mathbf{b}_2 = (2\pi/a)\hat{\mathbf{y}} ; \quad \mathbf{b}_3 = (2\pi/a)\hat{\mathbf{z}} . \quad (27b)$$

Here the reciprocal lattice is itself a simple cubic lattice, now of lattice constant $2\pi/a$.

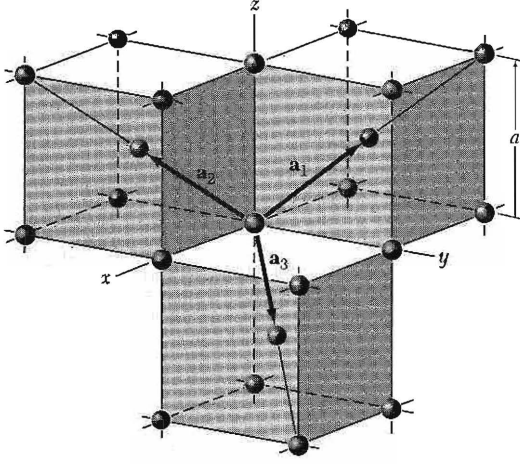


Figure 12 Primitive basis vectors of the body-centered cubic lattice.

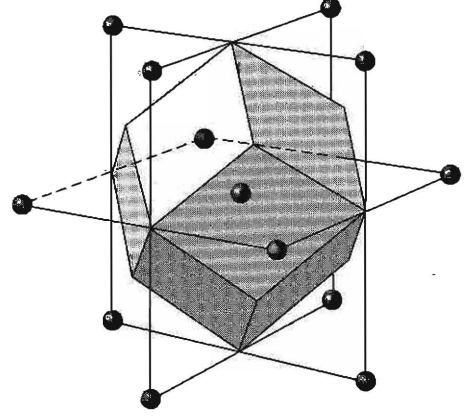


Figure 13 First Brillouin zone of the body-centered cubic lattice. The figure is a regular rhombic dodecahedron.

The boundaries of the first Brillouin zones are the planes normal to the six reciprocal lattice vectors $\pm \mathbf{b}_1, \pm \mathbf{b}_2, \pm \mathbf{b}_3$ at their midpoints:

$$\pm \frac{1}{2} \mathbf{b}_1 = \pm (\pi/a) \hat{\mathbf{x}} ; \quad \pm \frac{1}{2} \mathbf{b}_2 = \pm (\pi/a) \hat{\mathbf{y}} ; \quad \pm \frac{1}{2} \mathbf{b}_3 = \pm (\pi/a) \hat{\mathbf{z}} . \quad (28)$$

The six planes bound a cube of edge $2\pi/a$ and of volume $(2\pi/a)^3$; this cube is the first Brillouin zone of the sc crystal lattice.

Reciprocal Lattice to bcc Lattice

The primitive translation vectors of the bcc lattice (Fig. 12) are

$$\mathbf{a}_1 = \frac{1}{2} a (-\hat{\mathbf{x}} + \hat{\mathbf{y}} + \hat{\mathbf{z}}) ; \quad \mathbf{a}_2 = \frac{1}{2} a (\hat{\mathbf{x}} - \hat{\mathbf{y}} + \hat{\mathbf{z}}) ; \quad \mathbf{a}_3 = \frac{1}{2} a (\hat{\mathbf{x}} + \hat{\mathbf{y}} - \hat{\mathbf{z}}) , \quad (29)$$

where a is the side of the conventional cube and $\hat{\mathbf{x}}, \hat{\mathbf{y}}, \hat{\mathbf{z}}$ are orthogonal unit vectors parallel to the cube edges. The volume of the primitive cell is

$$V = |\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3| = \frac{1}{2} a^3 . \quad (30)$$

The primitive translations of the reciprocal lattice are defined by (13). We have, using (28),

$$\mathbf{b}_1 = (2\pi/a)(\hat{\mathbf{y}} + \hat{\mathbf{z}}) ; \quad \mathbf{b}_2 = (2\pi/a)(\hat{\mathbf{x}} + \hat{\mathbf{z}}) ; \quad \mathbf{b}_3 = (2\pi/a)(\hat{\mathbf{x}} + \hat{\mathbf{y}}) . \quad (31)$$

Note by comparison with Fig. 14 (p. 37) that these are just the primitive vectors of an fcc lattice, so that an fcc lattice is the reciprocal lattice of the bcc lattice.

The general reciprocal lattice vector is, for integral v_1, v_2, v_3 ,

$$\mathbf{G} = v_1 \mathbf{b}_1 + v_2 \mathbf{b}_2 + v_3 \mathbf{b}_3 = (2\pi/a)[(v_2 + v_3)\hat{\mathbf{x}} + (v_1 + v_3)\hat{\mathbf{y}} + (v_1 + v_2)\hat{\mathbf{z}}] . \quad (32)$$

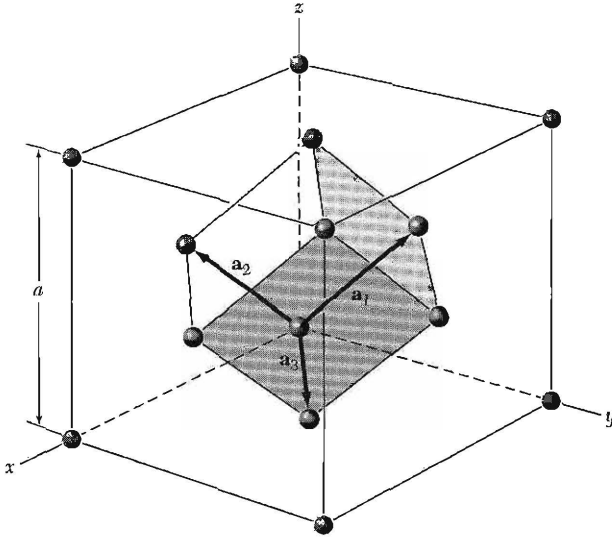


Figure 14 Primitive basis vectors of the face-centered cubic lattice.

The shortest \mathbf{G} 's are the following 12 vectors, where all choices of sign are independent:

$$(2\pi/a)(\pm\hat{y} \pm \hat{z}) ; \quad (2\pi/a)(\pm\hat{x} \pm \hat{z}) ; \quad (2\pi/a)(\pm\hat{x} \pm \hat{y}) . \quad (33)$$

One primitive cell of the reciprocal lattice is the parallelepiped described by the \mathbf{b}_1 , \mathbf{b}_2 , \mathbf{b}_3 defined by (31). The volume of this cell in reciprocal space is $\mathbf{b}_1 \cdot \mathbf{b}_2 \times \mathbf{b}_3 = 2(2\pi/a)^3$. The cell contains one reciprocal lattice point, because each of the eight corner points is shared among eight parallelepipeds. Each parallelepiped contains one-eighth of each of eight corner points (see Fig. 12).

Another primitive cell is the central (Wigner-Seitz) cell of the reciprocal lattice which is the first Brillouin zone. Each such cell contains one lattice point at the central point of the cell. This zone (for the bcc lattice) is bounded by the planes normal to the 12 vectors of Eq. (33) at their midpoints. The zone is a regular 12-faced solid, a rhombic dodecahedron, as shown in Fig. 13.

Reciprocal Lattice to fcc Lattice

The primitive translation vectors of the fcc lattice of Fig. 14 are

$$\mathbf{a}_1 = \frac{1}{2}a(\hat{y} + \hat{z}) ; \quad \mathbf{a}_2 = \frac{1}{2}a(\hat{x} + \hat{z}) ; \quad \mathbf{a}_3 = \frac{1}{2}a(\hat{x} + \hat{y}) . \quad (34)$$

The volume of the primitive cell is

$$V = |\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3| = \frac{1}{4}a^3 . \quad (35)$$

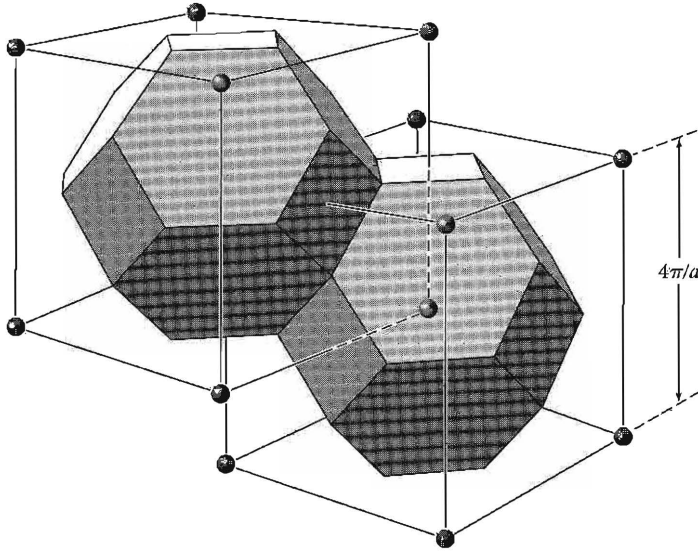


Figure 15 Brillouin zones of the face-centered cubic lattice. The cells are in reciprocal space, and the reciprocal lattice is body centered.

The primitive translation vectors of the lattice reciprocal to the fcc lattice are

$$\begin{aligned} \mathbf{b}_1 &= (2\pi/a)(-\hat{x} + \hat{y} + \hat{z}) ; & \mathbf{b}_2 &= (2\pi/a)(\hat{x} - \hat{y} + \hat{z}) ; \\ \mathbf{b}_3 &= (2\pi/a)(\hat{x} + \hat{y} - \hat{z}) . \end{aligned} \quad (36)$$

These are primitive translation vectors of a bcc lattice, so that the bcc lattice is reciprocal to the fcc lattice. The volume of the primitive cell of the reciprocal lattice is $4(2\pi/a)^3$.

The shortest \mathbf{G} 's are the eight vectors:

$$(2\pi/a)(\pm\hat{x} \pm \hat{y} \pm \hat{z}) . \quad (37)$$

The boundaries of the central cell in the reciprocal lattice are determined for the most part by the eight planes normal to these vectors at their midpoints. But the corners of the octahedron thus formed are cut by the planes that are the perpendicular bisectors of six other reciprocal lattice vectors:

$$(2\pi/a)(\pm 2\hat{x}) ; \quad (2\pi/a)(\pm 2\hat{y}) ; \quad (2\pi/a)(\pm 2\hat{z}) . \quad (38)$$

Note that $(2\pi/a)(2\hat{x})$ is a reciprocal lattice vector because it is equal to $\mathbf{b}_2 + \mathbf{b}_3$. The first Brillouin zone is the smallest bounded volume about the origin, the truncated octahedron shown in Fig. 15. The six planes bound a cube of edge $4\pi/a$ and (before truncation) of volume $(4\pi/a)^3$.

FOURIER ANALYSIS OF THE BASIS

When the diffraction condition $\Delta \mathbf{k} = \mathbf{G}$ of Eq. (21) is satisfied, the scattering amplitude (18) for a crystal of N cells may be written as

$$F_{\mathbf{G}} = N \int_{\text{cell}} dV n(\mathbf{r}) \exp(-i\mathbf{G} \cdot \mathbf{r}) = NS_{\mathbf{G}} . \quad (39)$$

The quantity $S_{\mathbf{G}}$ is called the **structure factor** and is defined as an integral over a single cell, with $\mathbf{r} = 0$ at one corner.

Often it is useful to write the electron concentration $n(\mathbf{r})$ as the superposition of electron concentration functions n_j associated with each atom j of the cell. If \mathbf{r}_j is the vector to the center of atom j , then the function $n_j(\mathbf{r} - \mathbf{r}_j)$ defines the contribution of that atom to the electron concentration at \mathbf{r} . The total electron concentration at \mathbf{r} due to all atoms in the single cell is the sum

$$n(\mathbf{r}) = \sum_{j=1}^s n_j(\mathbf{r} - \mathbf{r}_j) \quad (40)$$

over the s atoms of the basis. The decomposition of $n(\mathbf{r})$ is not unique, for we cannot always say how much charge density is associated with each atom. This is not an important difficulty.

The structure factor defined by (39) may now be written as integrals over the s atoms of a cell:

$$\begin{aligned} S_{\mathbf{G}} &= \sum_j \int dV n_j(\mathbf{r} - \mathbf{r}_j) \exp(-i\mathbf{G} \cdot \mathbf{r}) \\ &= \sum_j \exp(-i\mathbf{G} \cdot \mathbf{r}_j) \int dV n_j(\boldsymbol{\rho}) \exp(-i\mathbf{G} \cdot \boldsymbol{\rho}) , \end{aligned} \quad (41)$$

where $\boldsymbol{\rho} = \mathbf{r} - \mathbf{r}_j$. We now define the **atomic form factor** as

$$f_j = \int dV n_j(\boldsymbol{\rho}) \exp(-i\mathbf{G} \cdot \boldsymbol{\rho}) , \quad (42)$$

integrated over all space. If $n_j(\boldsymbol{\rho})$ is an atomic property, f_j is an atomic property.

We combine (41) and (42) to obtain the **structure factor of the basis** in the form

$$S_{\mathbf{G}} = \sum_j f_j \exp(-i\mathbf{G} \cdot \mathbf{r}_j) . \quad (43)$$

The usual form of this result follows on writing for atom j :

$$\mathbf{r}_j = x_j \mathbf{a}_1 + y_j \mathbf{a}_2 + z_j \mathbf{a}_3 , \quad (44)$$

as in (1.2). Then, for the reflection labelled by v_1, v_2, v_3 , we have

$$\begin{aligned}\mathbf{G} \cdot \mathbf{r}_j &= (v_1 \mathbf{b}_1 + v_2 \mathbf{b}_2 + v_3 \mathbf{b}_3) \cdot (x_j \mathbf{a}_1 + y_j \mathbf{a}_2 + z_j \mathbf{a}_3) \\ &= 2\pi(v_1 x_j + v_2 y_j + v_3 z_j) \quad ,\end{aligned}\quad (45)$$

so that (43) becomes

$$S_G(v_1 v_2 v_3) = \sum_j f_j \exp[-i2\pi(v_1 x_j + v_2 y_j + v_3 z_j)] \quad . \quad (46)$$

The structure factor S need not be real because the scattered intensity will involve S^*S , where S^* is the complex conjugate of S so that S^*S is real.

Structure Factor of the bcc Lattice

The bcc basis referred to the cubic cell has identical atoms at $x_1 = y_1 = z_1 = 0$ and at $x_2 = y_2 = z_2 = \frac{1}{2}$. Thus (46) becomes

$$S(v_1 v_2 v_3) = f[1 + \exp[-i\pi(v_1 + v_2 + v_3)]] \quad , \quad (47)$$

where f is the form factor of an atom. The value of S is zero whenever the exponential has the value -1 , which is whenever the argument is $-i\pi \times (\text{odd integer})$. Thus we have

$$\begin{aligned}S &= 0 && \text{when } v_1 + v_2 + v_3 = \text{odd integer} ; \\ S &= 2f && \text{when } v_1 + v_2 + v_3 = \text{even integer} .\end{aligned}$$

Metallic sodium has a bcc structure. The diffraction pattern does not contain lines such as (100), (300), (111), or (221), but lines such as (200), (110), and (222) will be present; here the indices $(v_1 v_2 v_3)$ are referred to a cubic cell. What is the physical interpretation of the result that the (100) reflection vanishes? The (100) reflection normally occurs when reflections from the planes that bound the cubic cell differ in phase by 2π . In the bcc lattice there is an intervening plane (Fig. 16) of atoms, labeled the second plane in the figure, which is equal in scattering power to the other planes. Situated midway between them, it gives a reflection retarded in phase by π with respect to the first plane, thereby canceling the contribution from that plane. The cancellation of the (100) reflection occurs in the bcc lattice because the planes are identical in composition. A similar cancellation can easily be found in the hcp structure.

Structure Factor of the fcc Lattice

The basis of the fcc structure referred to the cubic cell has identical atoms at 000; $0\frac{11}{22}$; $\frac{1}{2}0\frac{1}{2}$; $\frac{1}{2}\frac{1}{2}0$. Thus (46) becomes

$$\begin{aligned}S(v_1 v_2 v_3) &= f[1 + \exp[-i\pi(v_2 + v_3)] + \exp[-i\pi(v_1 + v_3)] \\ &\quad + \exp[-i\pi(v_1 + v_2)]] \quad .\end{aligned}\quad (48)$$

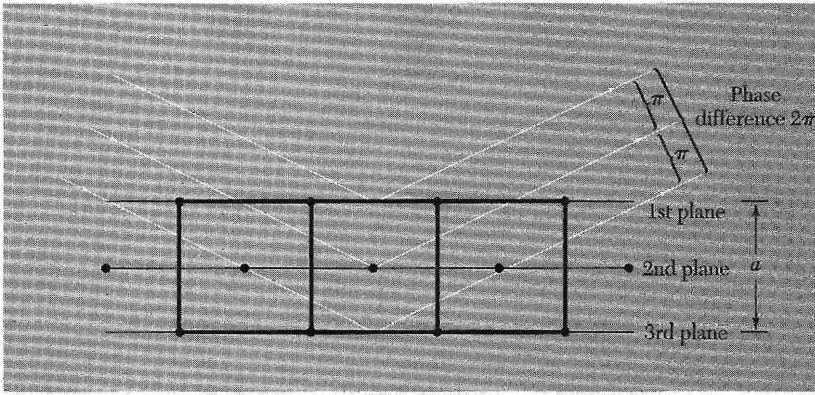


Figure 16 Explanation of the absence of a (100) reflection from a body-centered cubic lattice. The phase difference between successive planes is π , so that the reflected amplitude from two adjacent planes is $1 + e^{-i\pi} = 1 - 1 = 0$.

If all indices are even integers, $S = 4f$; similarly if all indices are odd integers. But if only one of the integers is even, two of the exponents will be odd multiples of $-i\pi$ and S will vanish. If only one of the integers is odd, the same argument applies and S will also vanish. Thus in the fcc lattice no reflections can occur for which the indices are partly even and partly odd.

The point is beautifully illustrated by Fig. 17: both KCl and KBr have an fcc lattice, but $n(\mathbf{r})$ for KCl simulates an sc lattice because the K^+ and Cl^- ions have equal numbers of electrons.

Atomic Form Factor

In the expression (46) for the structure factor, there occurs the quantity f_j , which is a measure of the scattering power of the j th atom in the unit cell. The value of f involves the number and distribution of atomic electrons, and the wavelength and angle of scattering of the radiation. We now give a classical calculation of the scattering factor.

The scattered radiation from a single atom takes account of interference effects within the atom. We defined the form factor in (42):

$$f_j = \int dV n_j(\mathbf{r}) \exp(-i\mathbf{G} \cdot \mathbf{r}) , \quad (49)$$

with the integral extended over the electron concentration associated with a single atom. Let \mathbf{r} make an angle α with \mathbf{G} ; then $\mathbf{G} \cdot \mathbf{r} = Gr \cos \alpha$. If the electron distribution is spherically symmetric about the origin, then

$$\begin{aligned} f_j &\equiv 2\pi \int dr r^2 d(\cos \alpha) n_j(r) \exp(-iGr \cos \alpha) \\ &= 2\pi \int dr r^2 n_j(r) \cdot \frac{e^{iGr} - e^{-iGr}}{iGr} , \end{aligned}$$

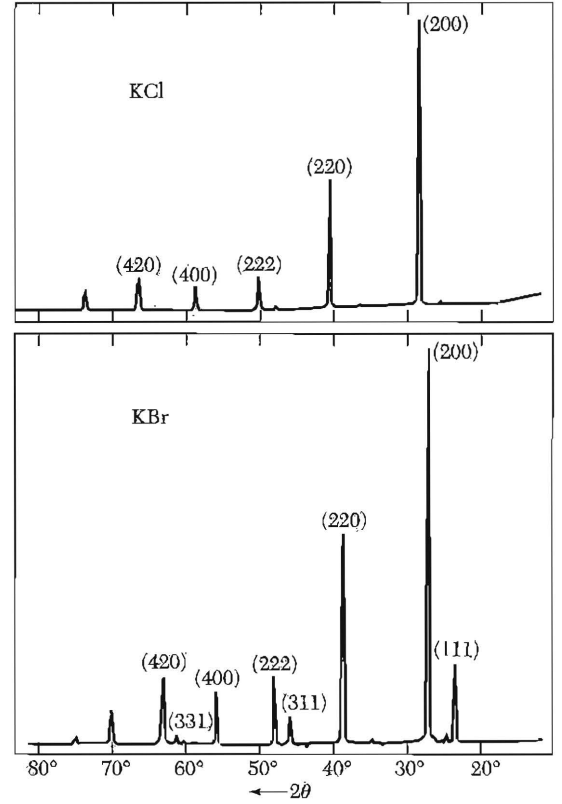


Figure 17 Comparison of x-ray reflections from KCl and KBr powders. In KCl the numbers of electrons of K^+ and Cl^- ions are equal. The scattering amplitudes $f(K^+)$ and $f(Cl^-)$ are almost exactly equal, so that the crystal looks to x-rays as if it were a monatomic simple cubic lattice of lattice constant $a/2$. Only even integers occur in the reflection indices when these are based on a cubic lattice of lattice constant a . In KBr the form factor of Br^- is quite different to that of K^+ , and all reflections of the fcc lattice are present. (Courtesy of R. van Norderstrand.)

after integration over $d(\cos \alpha)$ between -1 and 1 . Thus the form factor is given by

$$f_j = 4\pi \int dr n_j(r) r^2 = \frac{\sin Gr}{Gr} \quad (50)$$

If the same total electron density were concentrated at $r = 0$, only $Gr = 0$ would contribute to the integrand. In this limit $(\sin Gr)/Gr = 1$, and

$$f_j = 4\pi \int dr n_j(r) r^2 = Z, \quad (51)$$

the number of atomic electrons. Therefore f is the ratio of the radiation amplitude scattered by the actual electron distribution in an atom to that scattered by one electron localized at a point. In the forward direction $G = 0$, and f reduces again to the value Z .

The overall electron distribution in a solid as seen in x-ray diffraction is fairly close to that of the appropriate free atoms. This statement does not mean that the outermost or valence electrons are not redistributed somewhat in forming the solid; it means only that the x-ray reflection intensities are represented well by the free atom values of the form factors and are not very sensitive to small redistributions of the electrons.

SUMMARY

- Various statements of the Bragg condition:

$$2d \sin \theta = n\lambda ; \quad \Delta \mathbf{k} = \mathbf{G} ; \quad 2\mathbf{k} \cdot \mathbf{G} = G^2 .$$

- Laue conditions:

$$\mathbf{a}_1 \cdot \Delta \mathbf{k} = 2\pi v_1 ; \quad \mathbf{a}_2 \cdot \Delta \mathbf{k} = 2\pi v_2 ; \quad \mathbf{a}_3 \cdot \Delta \mathbf{k} = 2\pi v_3 .$$

- The primitive translation vectors of the reciprocal lattice are

$$\mathbf{b}_1 = 2\pi \frac{\mathbf{a}_2 \times \mathbf{a}_3}{\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3} ; \quad \mathbf{b}_2 = 2\pi \frac{\mathbf{a}_3 \times \mathbf{a}_1}{\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3} ; \quad \mathbf{b}_3 = 2\pi \frac{\mathbf{a}_1 \times \mathbf{a}_2}{\mathbf{a}_1 \cdot \mathbf{a}_2 \times \mathbf{a}_3} .$$

Here $\mathbf{a}_1, \mathbf{a}_2, \mathbf{a}_3$ are the primitive translation vectors of the crystal lattice.

- A reciprocal lattice vector has the form

$$\mathbf{G} = v_1 \mathbf{b}_1 + v_2 \mathbf{b}_2 + v_3 \mathbf{b}_3 ,$$

where v_1, v_2, v_3 are integers or zero.

- The scattered amplitude in the direction $\mathbf{k}' = \mathbf{k} + \Delta \mathbf{k} = \mathbf{k} + \mathbf{G}$ is proportional to the geometrical structure factor:

$$S_{\mathbf{G}} \equiv \sum_j f_j \exp(-i\mathbf{r}_j \cdot \mathbf{G}) = \sum_j f_j \exp[-i2\pi(x_j v_1 + y_j v_2 + z_j v_3)] ,$$

where j runs over the s atoms of the basis, and f_j is the atomic form factor (49) of the j th atom of the basis. The expression on the right-hand side is written for a reflection $(v_1 v_2 v_3)$, for which $\mathbf{G} = v_1 \mathbf{b}_1 + v_2 \mathbf{b}_2 + v_3 \mathbf{b}_3$.

- Any function invariant under a lattice translation \mathbf{T} may be expanded in a Fourier series of the form

$$n(\mathbf{r}) = \sum_{\mathbf{G}} n_{\mathbf{G}} \exp(i\mathbf{G} \cdot \mathbf{r}) .$$

- The first Brillouin zone is the Wigner-Seitz primitive cell of the reciprocal lattice. Only waves whose wavevector \mathbf{k} drawn from the origin terminates on a surface of the Brillouin zone can be diffracted by the crystal.

<i>Crystal lattice</i>	<i>First Brillouin zone</i>
Simple cubic	Cube
Body-centered cubic	Rhombic dodecahedron (Fig. 13)
Face-centered cubic	Truncated octahedron (Fig. 15)

Problems

1. **Interplanar separation.** Consider a plane hkl in a crystal lattice. (a) Prove that the reciprocal lattice vector $\mathbf{G} = h\mathbf{b}_1 + k\mathbf{b}_2 + l\mathbf{b}_3$ is perpendicular to this plane. (b) Prove that the distance between two adjacent parallel planes of the lattice is $d(hkl) = 2\pi/|\mathbf{G}|$. (c) Show for a simple cubic lattice that $d^2 = a^2/(h^2 + k^2 + l^2)$.